

Dual Phase Steels



Disclaimer

"The information in this presentation has been prepared by CBMM - CBMM Europe B.V. (the "Company") with the only purposes of introducing the company's activities, in 2017. This document and its contents are confidential and are being provided to you solely for your information and may not be reproduced, retransmitted, further distributed to any other person or published, in whole or in part, by any medium or in any form for any purpose. The opinions presented herein are based on information gathered at the time of writing and are subject to change without notice. The Company relies on information obtained from sources believed to be reliable but does not guarantee its accuracy or completeness. This presentation may contain certain forward-looking statements and information relating to the Company and its affiliates, related companies, directors, officers, shareholders, agents or employees that reflect the current views and/or expectations of the Company and its management with respect to its performance, business and future events. Forwardlooking statements include, without limitation, any statement that may predict, forecast, indicate or imply future results, performance or achievements, and may contain words like "believe", "anticipate", "expect", "envisages", "will likely result", or any other words or phrases of similar meaning. Such statements are subject to a number of risks, uncertainties and assumptions. We caution you that a number of important factors could cause actual outcomes to differ materially from the plans, objectives, expectations, estimates and intentions expressed in this presentation. In any event, neither the Company nor any of its affiliates, related companies, directors, officers, shareholders, agents or employees are or will be liable to any third party for any investment or business decision made or action taken in reliance on the information and statements contained in this presentation or for any consequential, special or similar damages. The information contained in this presentation has not been independently verified. This presentation and its contents are proprietary information and may not be reproduced or otherwise disseminated in whole or in part without the Company prior written consent."



Contents


- What are Dual Phase steels?
- Benefits of Dual Phase steels
- Applications for Niobium Dual Phase Steels
- Challenges of Dual Phase steels
- The Niobium Solution
- Niobium advantage



What are Dual Phase Steels

- Class of steels which can vary in strength from 550MPA to >1,000MPA
- Produced by hot or cold rolling followed by controlled thermal processing to achieve a dual phase microstructure
- Attractive because they combine strength and ductility
- Widely used in automotive industry, though uptake impacted by production issues

Dual Phase Microstructure

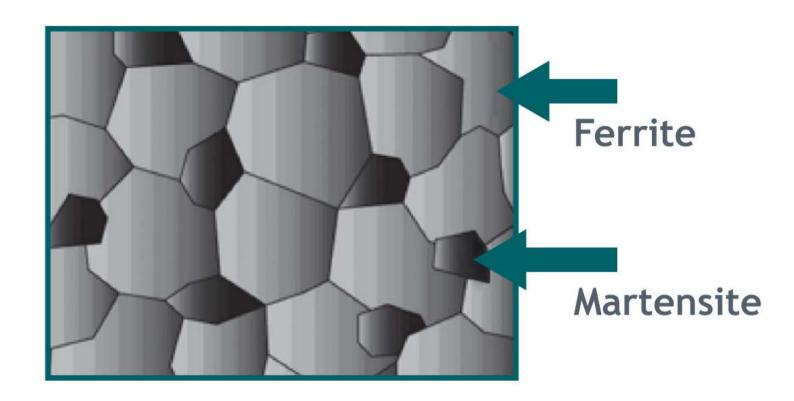


Example of a microstructure of a dual phase steel, showing the martensite (dark) and ferrite (light) phases


Source: Advanced High-Strength Steels Application Guidelines V5.0, May 2014, WorldAutoSteel, editors: S. Keeler and M. Kimchi



Benefits of Dual Phase Steels

- Combination of strength and ductility creates a number of potential benefits
 - Lightweighting
 - Energy (crash) absorption
 - Increased production efficiency (cold workability)
- Simpler processing and low level of alloying compared to CP, TRIP of TWIP steels

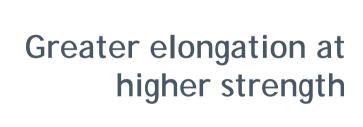


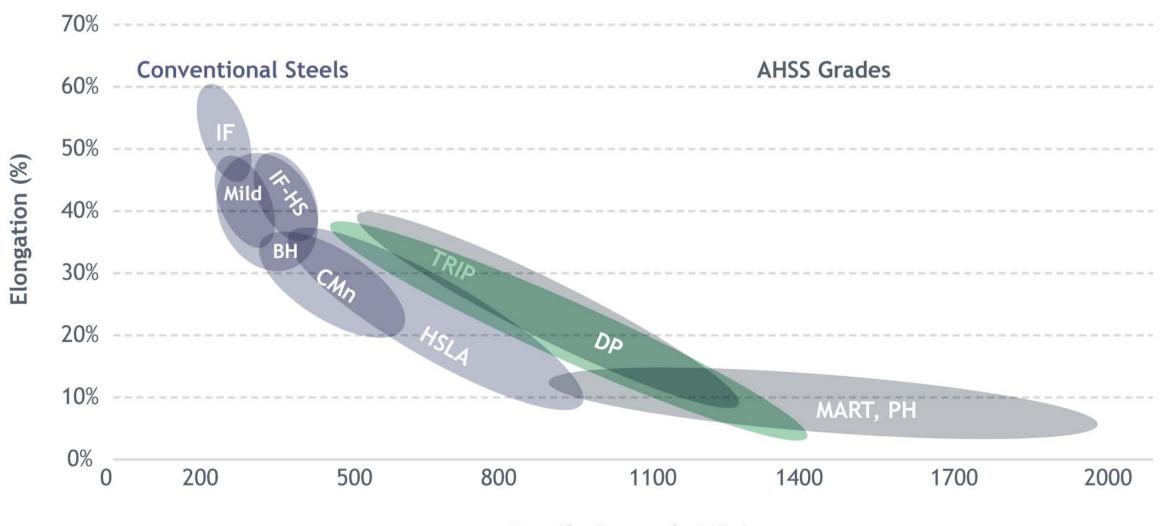

Tensile Strength (MPa)




Applications

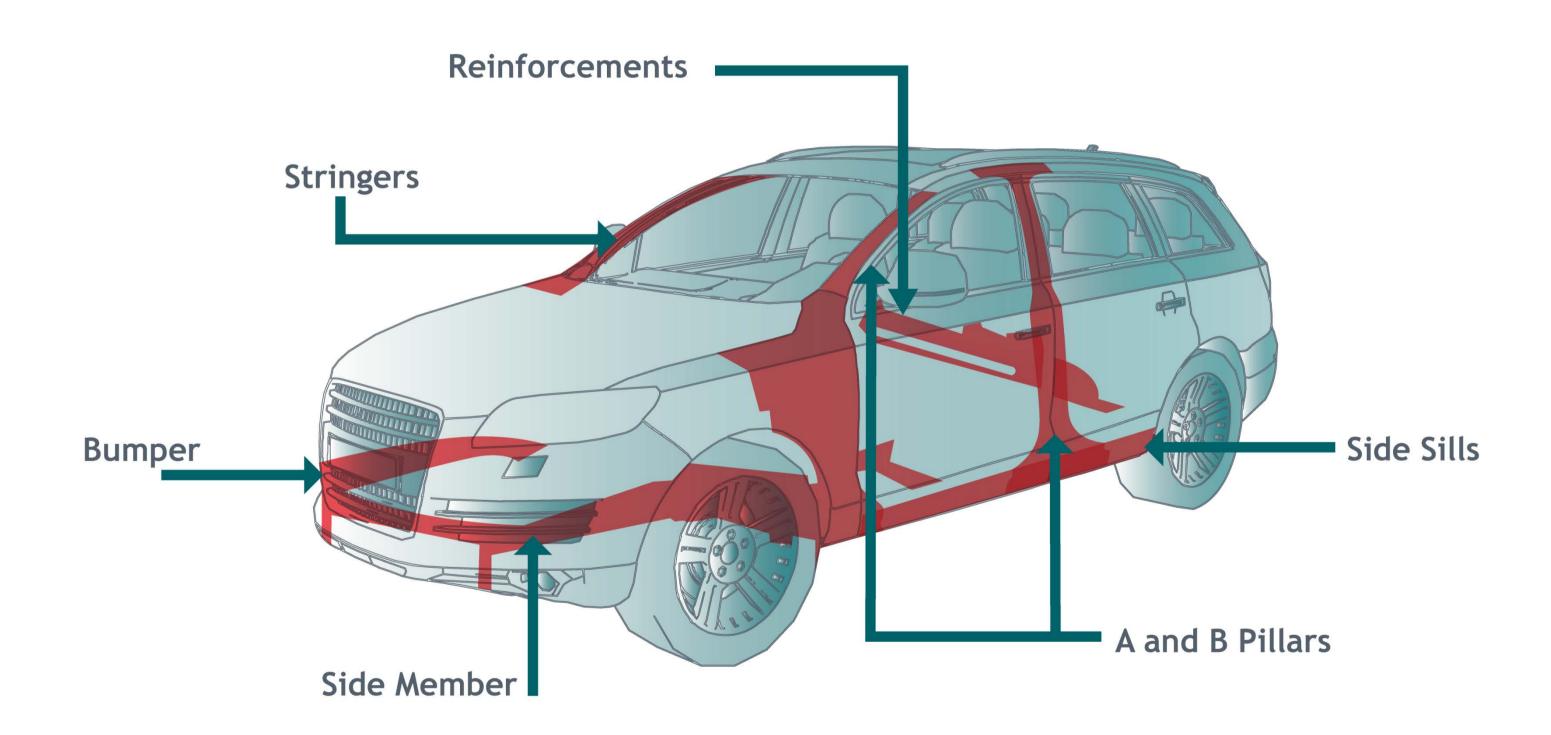



Challenges of Dual Phase Steels

- Dual Phase steels designed to produce press stamped parts with complex shapes
- However, in practice encountered problems during forming which caused parts to fail
 - Non-uniform shaping which caused cracking
 - Localised stretching issues causing parts to fail
- Niobium micro-alloying developed to solve these problems by improving local formability

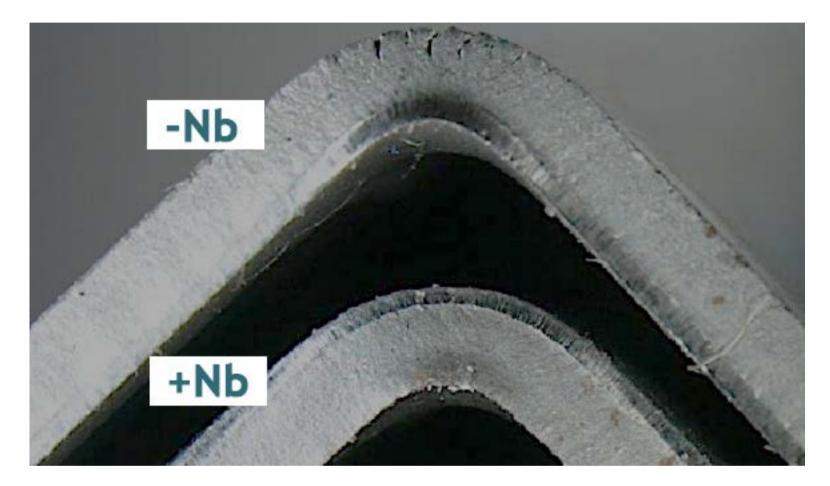


Source: H. Mohrbacher. Intl. Symp. on New Developments in Advanced High-Strength Sheet Steels, AIST, 2013, p. 319-329




The Niobium Solution

Niobium grain refinement addresses the problems of Dual Phase steels

- Results in significantly improved formability
 - Bendability
 - Hole-expansion ratio
- Can also improve
 - Strength
 - Weldability
 - Process robustness

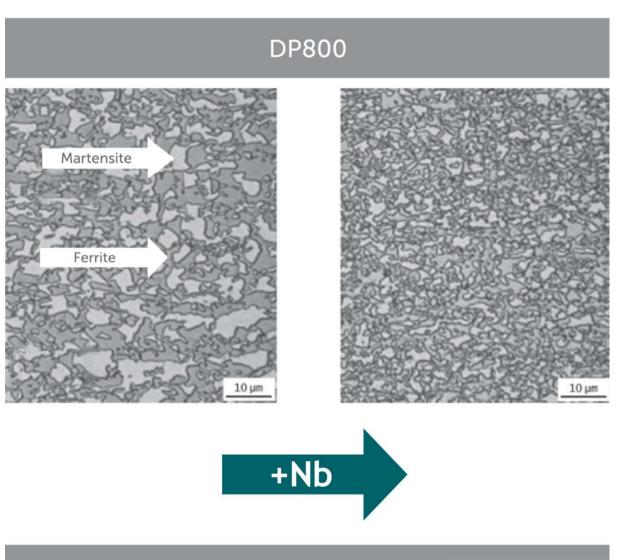

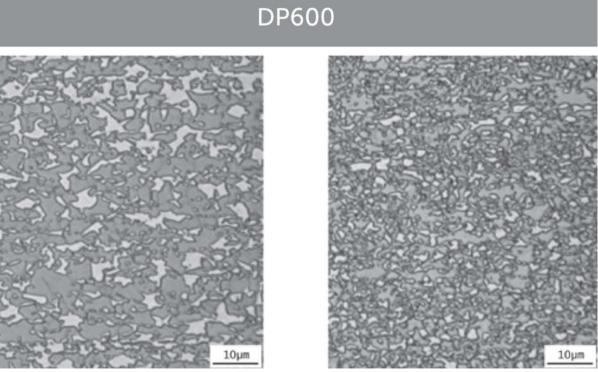


Source: H. Mohrbacher. Intl. Symp. on New Developments in Advanced High-Strength Sheet Steels, AIST, 2013, p. 319-329




How Niobium Improves Formability


By refining the microstructure, Niobium:

- Prevents Martensite areas from becoming too large and brittle*
- Prevents crack propagation by refining martensite areas and stopping them from clustering
- Consequently Niobium Dual Phase steels
 - Are easier to bend
 - Can be stretched further (elongation)
 - Are easier to work when cold (n-value)

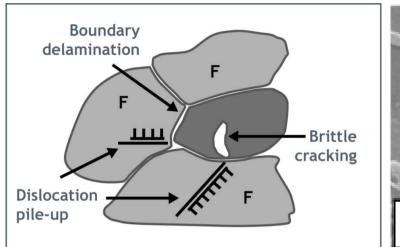

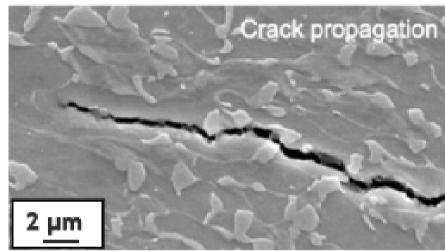

Source: Reference: H. Mohrbacher. Intl. Symp. on New Developments in Advanced High-Strength Sheet Steels, AIST, 2013, p. 319-329

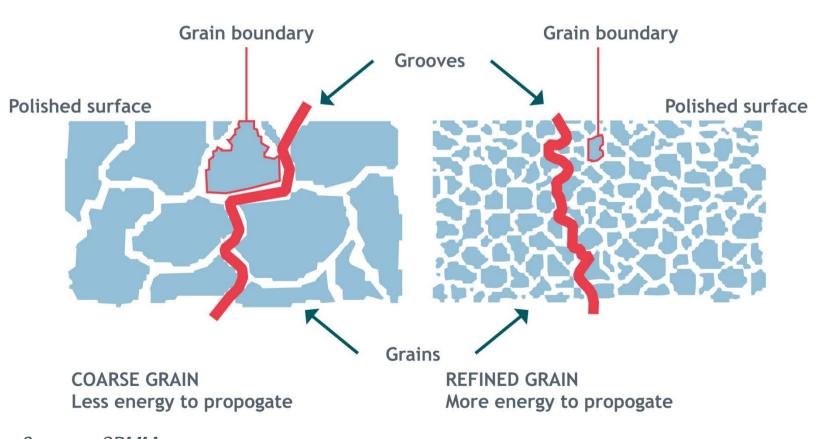

Source: CBMM


^{*} Also partly avoiding martensite transforming into bainite




Significant Increase in Formability – Bending Angle

Microalloying of Niobium at 0.01/0.03% with standard Dual Phase steels significantly improves formability

- Increases angle material can be bent before it fails reducing cracking from 90° to 120°
- Reduces the minimum bending radius enabling design optimisation

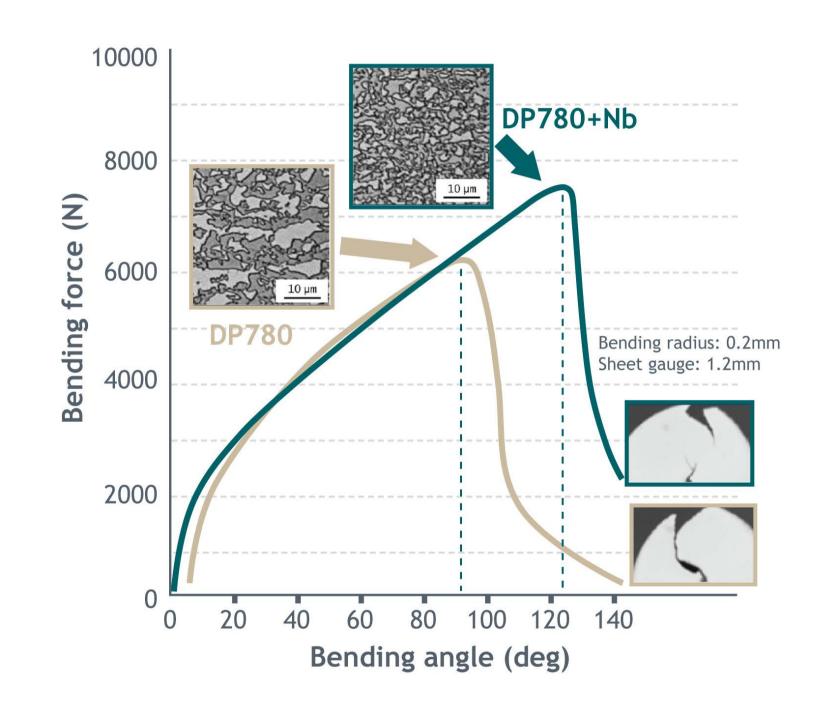

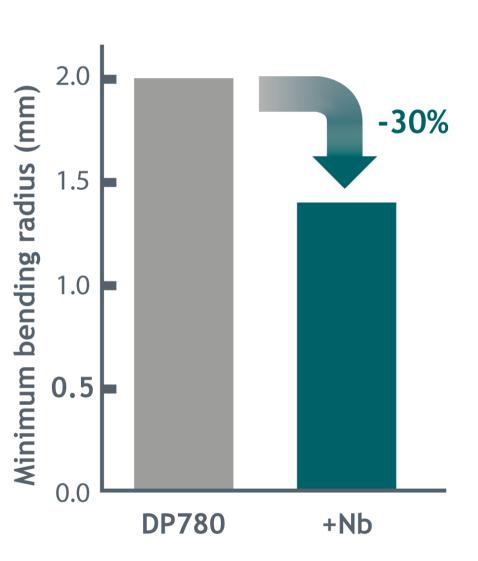


Source: H. Mohrbacher. Intl. Symp. on New Developments in Advanced High-Strength Sheet Steels, AIST, 2013, p. 319-329



Significant Increase in Formability – Hole Expansion

 By refining martensite areas Niobium improves hole expansion

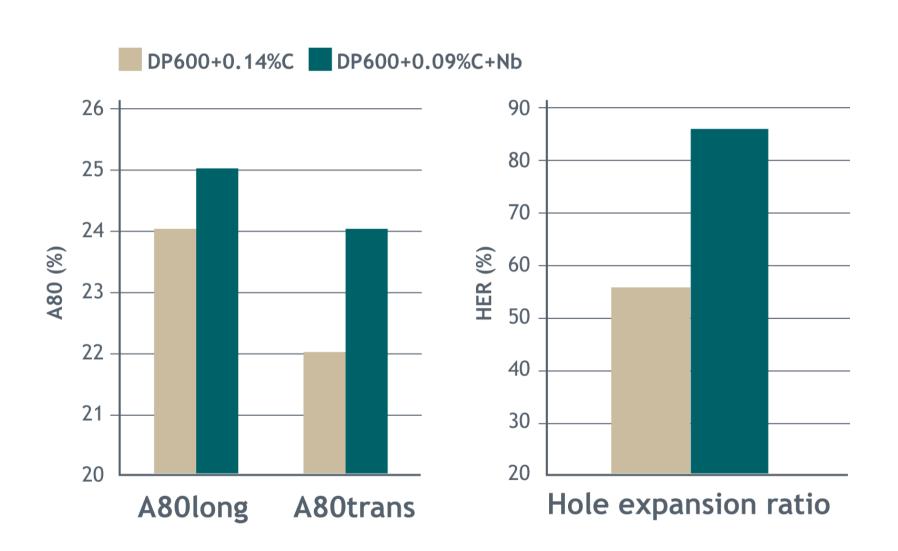

Hole expansion $\frac{2\mu m}{Crack propogation}$ Punch the hole $\lambda = \frac{d_f - d_0}{d_0} \times 100$ Voids and microcracks


Source: Improvement of hole expansion ratio of low carbon DP600+Nb in comparison with conventional DP600+0.14%C

Source: J. Bian. Niobium microalloying in the automotive steels for light-weighting. South East Asia Iron and Steel Institute 2014



Additional Benefits

- Strength: Niobium grain refinement increases the tensile strength of steel
- Elongation: In addition to Niobium's grain refinement effect, increased tensile strength reduces need for martensite
- Welding: Carbon is major cause of welding problems and can be quite high in DP steels (up to 0.2%)
 Niobium grain refinement reduces welding embrittlement issues brought by higher carbon

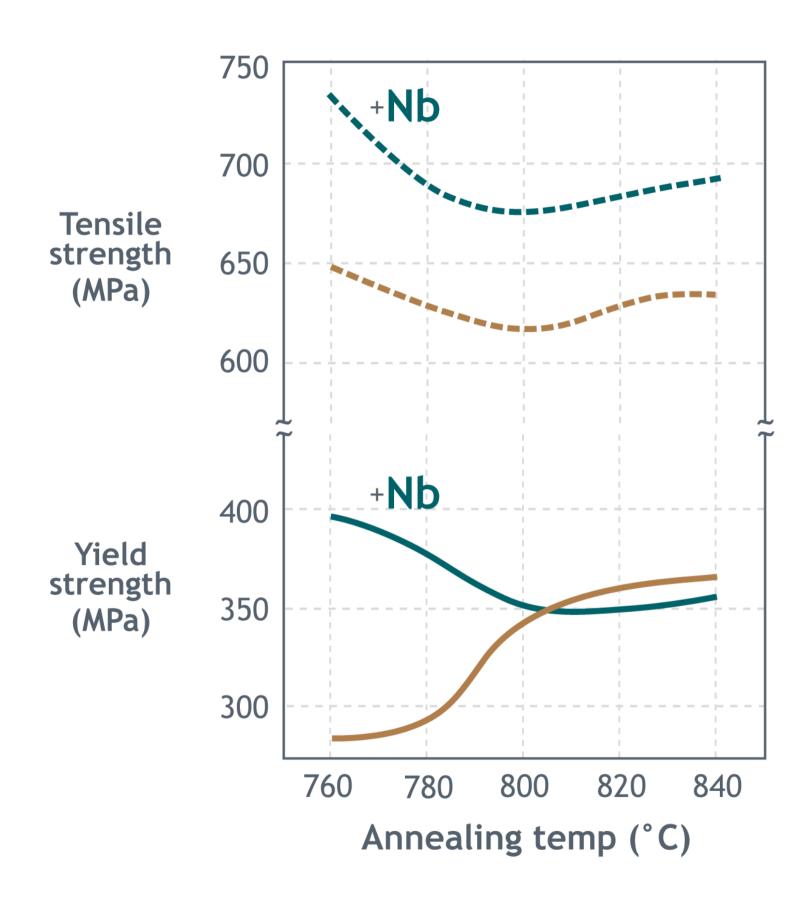

Source: H. Mohrbacher. Intl. Symp. on New Developments in Advanced High-Strength Sheet Steels, AIST, 2013, p. 319-329



Niobium advantage

- Niobium usage creates a more formable Dual Phase steel, which is
 - Easy to bend, stamp and punch
 - Easy for existing production facilities to use
 - Simpler to process and with lower levels of alloying compared to CP, TRIP or TWIP steels
- Enables
 - Optimised parts
 - Production efficiencies
 - Reduced defects and increased production reliability
 - Improved crash performance